

ARKEMA

KYNAR 500[®]FSF[®]

Case Studies in Performance

**PVDF-BASED COATINGS VERSUS
POLYESTER POWDER AND OTHER COATINGS**



Test Panels on Exposure at Arkema's Sub-Tropical Exposure Station

THE TRUTH IS ON THE TEST FENCE.

Metal has rapidly become the material of choice for exterior use due to its rugged durability, design versatility and aesthetic possibilities. However, for all its bravado and beauty, metal doesn't necessarily have a tough skin and is only available in a single color. To be both functional and decorative, metal must be coated with a finish that beautifies with color and doesn't chalk; that won't lose its color and sheen; that won't pit, chip or age before its time.

Kynar 500® resin-based finishes are available worldwide through a strict licensing program. This licensed distribution ensures the quality, consistency and high performance of Kynar 500® resin-based coatings.

PERFORMANCE TESTING

Objective

To measure and compare the performance of Kynar 500® resin-based coating systems with competitive coatings for their resistance to weather.

Background

Panels coated with liquid Kynar 500® resin-based coatings and powder coated with other resin systems were exposed on a South Florida test fence for 10 to 17 years. The panels were evaluated periodically during exposure for chalk, gloss and color changes. See table below.


Conclusion

Kynar 500® resin-based coatings outperform polyester powder, urethane, silicone polyester and acrylic coatings in every category: better color retention, better resistance to chalking. The proof is in the pictures of the coated panels. Just compare the unexposed portion (top panels) with the exposed portion (bottom panels). Performance as promised. Time after time. Kynar 500® resin-based coatings.


FLORIDA EXPOSURE 45° SOUTH. - 17 YEARS EXPOSURE.




Kynar 500®
Bronze

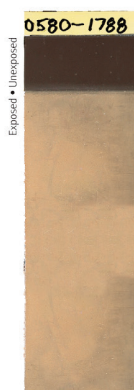


Polyester
Powder
Bronze

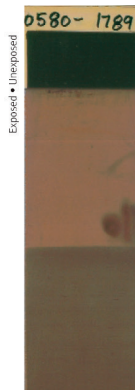


Silicone
Polyester
Bronze

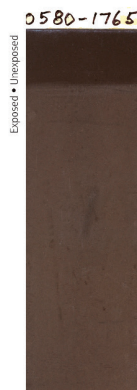

Kynar 500®
Bronze

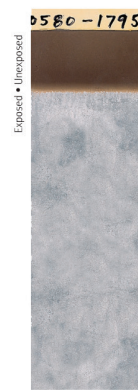

Acrylic
Bronze

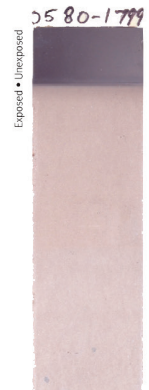

Urethane
Bronze

FLORIDA EXPOSURE 45° SOUTH. - 10 YEARS EXPOSURE.



Kynar 500®
Yellow



Polyester
Powder
Yellow




Kynar 500®
Red





Polyester
Powder
Orange



Kynar 500®
Bronze

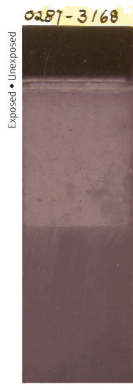

Polyester
Powder
Bronze

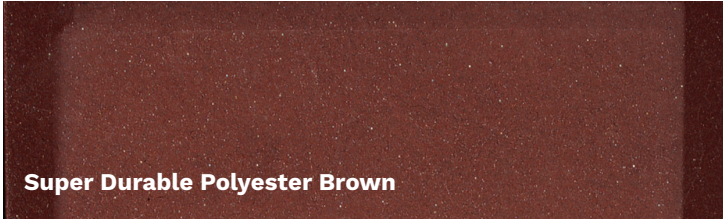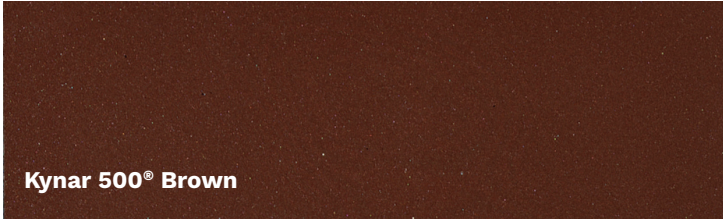


Kynar 500° -based coatings are typically solvent-based, but are often confused with powder coatings through the following question, “How does a Kynar 500° -based coating compare to a powder coating?” The easiest answer is that all coating systems, whether liquid or powder, contain a specific resin that acts as the first line of defense against weathering. Ultimately, the resin determines the durability. Kynar 500° -based coating is a resin commonly known as polyvinylidene fluoride. Other coating resins include acrylic, polyester, silicone polyester and urethane. In today’s market, liquid Kynar 500° -based coatings are the most common, but Kynar 500° -based coating is also available as a

powder coating. Whether you are looking for a liquid coating or a powder coating, the key to product performance is the resin chemistry. For the ultimate long-term durability, time has shown Kynar 500° PVDF resin is the one to choose.

In color-matched accelerated weathering tests, shown above, Kynar 500° -based coating panels clearly outperformed the latest “super durable polyester” powder technology. Contact us at www.kynar500.com for more information on Kynar 500° -based coatings.

PANEL NO.	DESCRIPTION	EXPOSURE TIME	ORIGINAL GLOSS 60°	FINAL GLOSS 60°	COLOR CHANGE ΔE	CHALK (EXPOSED) ASTM D-4214
1764	Kynar 500°, Bronze	17 years	31	8	6.71	8
1788	Silicone Polyester, Bronze	17 years	44	1	27.06	4
1789	Silicone Polyester, Bronze	17 years	34	1	36.11	4
1765	Kynar 500°, Bronze	17 years	30	10	8.74	8
1795	Acrylic, Bronze	17 years	26	coating worn to substrate		
1799	Urethane, Bronze	17 years	36	1	38.26	6
3157	Kynar 500°, Yellow	10 years	15	15	5.35	10
3156	Polyester Powder, Yellow	10 years	28	3	23.37	6
3161	Kynar 500°, Red	10 years	52	36	8.77	10
3160	Polyester Powder, Orange	10 years	34	1	24.66	6
3169	Kynar 500°, Bronze	10 years	43	22	4.79	10
3168	Polyester Powder, Bronze	10 years	38	1	10.91	6

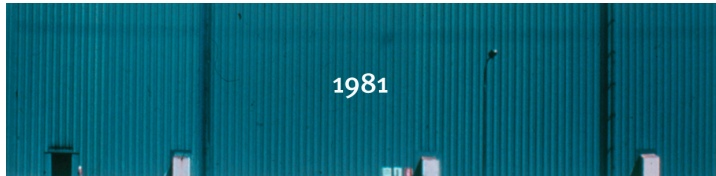

1981

Kynar 500	Acrylic	Polyester	Kynar 500	Silicone Polyester
-----------	---------	-----------	-----------	--------------------



1995

CASE STUDY: TAIYO STEEL

In 1981 in Funabashi Japan, Taiyo Steel Co., Ltd. built a plant for their new coil coating line employing metal walls. A decision was made to make the south wall an industrial test fence, to evaluate the outdoor weatherability of Taiyo Steel’s precoated metal products. Ten meter high steel panels were coated with acrylic, polyester, silicone polyester and Kynar 500° resin-based coatings.

In just two short years, there was a significant difference in color retention, gloss retention and chalk resistance between Kynar 500° resin-based coatings and other systems.

After fourteen years, the Kynar 500° resin-based coating was the only system that kept its original appearance, clearly outperforming the other coatings year-in and year-out.



Headquarters: Arkema France

420 rue d'Estienne d'Orves
92705 Colombes Cedex
France
T +33 (0)1 49 00 80 80

Arkema Inc.

900 1st Ave,
King of Prussia, PA 19406
United States
T +1 610 878 6500

Legal Disclaimer: All information contained herein is believed to be accurate as of the date of publication, is provided "as-is" and is subject to change without notice. This is not a warranty, an agreement, or substitute for expert or professional advice. Arkema Inc. ("Company") expressly disclaims and assumes no liability for the use of the products or reliance on this information. It is the sole responsibility of the user to determine the suitability of any products for user's application(s). NO WARRANTY OF FITNESS FOR ANY PARTICULAR PURPOSE OR ANY OTHER WARRANTY, EXPRESS OR IMPLIED (INCLUDING SUITABILITY FOR USE IN ANY MEDICAL DEVICE OR MEDICAL APPLICATION), IS MADE CONCERNING THE PRODUCTS OR THE INFORMATION PROVIDED HEREIN. The information provided relates only to the specific products designated herein and may not be valid where such products are used in combination with other materials or in any process. The performance of the product, its shelf life, and application characteristics depends on many variables, and changes in these variables can impact product performance. You are responsible to test the suitability of any product in advance for any intended use or application and before commercialization. Nothing herein shall be construed as a license for the use of any product in a manner that might infringe any patent and it should not be construed as an inducement to infringe any patent. Please carefully review the Safety Data Sheet for the product.

The Company adheres to a strict policy that applies to the use of any of its products in medical device applications. This policy can be found at <https://www.arkema.com/global/en/social-responsibility/innovation-and-sustainable-solutions/responsible-product-management/medical-device-policy/> which is incorporated herein by reference and made a part hereof. Except as expressly authorized, the Company (i) has designated specific medical grade compositions for products used in medical device applications and Company products not so designated are not authorized for use in medical device applications and (ii) strictly prohibits the use of any of its products in medical device applications that are implanted in the body or in contact with bodily fluids or tissues for greater than 30 days. The Company does not design, manufacture and/or directly sell any medical devices. The Company does not co-design, or offer assistance to any purchaser of its products, in their design, manufacture and/or sale of products for medical devices. It is the sole responsibility of the manufacturer of medical devices to determine the suitability of all raw material, products and components, including any medical grade products, in order to ensure that the medical device is safe for end-use and complies with all applicable legal and regulatory requirements and to conduct all necessary tests and inspections.